

AD-A207 183

FINAL REPORT

DATE 1988

EVT NO. 14-88

MIL-STD-1660 TEST OF
MO INDUSTRIES ALUMINUM
2,200 LB. PALLET

DTIC
S ELECTE D
APR 25 1989
E

Prepared for:

U.S. Army Armament Research,
Development and Engineering Center
ATTN: SMCAR-AEP
Picatinny Arsenal, NJ 07801-5000

Distribution Unlimited

MO Industries, Whippany, NJ

EVALUATION DIVISION
SAVANNA, ILLINOIS 61074-9638

US ARMY
ARMAMENT
MUNITIONS
CHEMICAL COMMAND

US ARMY DEFENSE AMMUNITION
CENTER AND SCHOOL

4 25 047

AVAILABILITY NOTICE

A copy of this report is furnished each attendee on automatic distribution. Additional copies or authority for reprinting may be obtained by written request from Director, U.S. Army Defense Ammunition Center and School. ATTN: SMCAC-DEV, Savanna, IL 61074-9639.

DISTRIBUTION INSTRUCTIONS

Destroy this report when no longer needed. Do not return.

* * *

Citation of trade names in this report does not constitute an official endorsement.

* * *

The information contained herein will not be used for advertising purposes.

REPORT DOCUMENTATION PAGE				Form Approved OMB No. 0704-0188	
1a. REPORT SECURITY CLASSIFICATION UNCLASSIFIED			1b. RESTRICTIVE MARKINGS		
2a. SECURITY CLASSIFICATION AUTHORITY			3. DISTRIBUTION / AVAILABILITY OF REPORT		
2b. DECLASSIFICATION / DOWNGRADING SCHEDULE					
4. PERFORMING ORGANIZATION REPORT NUMBER(S) EVT 14-88			5. MONITORING ORGANIZATION REPORT NUMBER(S)		
6a. NAME OF PERFORMING ORGANIZATION U.S. Army Defense Ammunition Center and School		6b. OFFICE SYMBOL (If applicable) SMCAC-DEV	7a. NAME OF MONITORING ORGANIZATION U.S. Army Armament Research, Development and Engineering Center		
6c. ADDRESS (City, State, and ZIP Code) Savanna, IL 61074-9639		7b. ADDRESS (City, State, and ZIP Code) ATTN: SMCAR-AEP Picatinny Arsenal, NJ 07801-5000			
8a. NAME OF FUNDING / SPONSORING ORGANIZATION MO Industries		8b. OFFICE SYMBOL (If applicable)	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER		
8c. ADDRESS (City, State, and ZIP Code) Whippany, NJ		10. SOURCE OF FUNDING NUMBERS			
		PROGRAM ELEMENT NO.	PROJECT NO.	TASK NO.	WORK UNIT ACCESSION NO.
11. TITLE (Include Security Classification) MIL-STD-1660 Test of MO Industries Aluminum 2,200-lb Pallet					
12. PERSONAL AUTHOR(S) A. C. McIntosh, Jr.					
13a. TYPE OF REPORT FINAL		13b. TIME COVERED FROM _____ TO _____	14. DATE OF REPORT (Year, Month, Day) 1988 February		15. PAGE COUNT 17
16. SUPPLEMENTARY NOTATION					
17. COSATI CODES			18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)		
FIELD	GROUP	SUB-GROUP	MIL-STD-1660		
			metal pallet		
			ammunition transportation		
19. ABSTRACT (Continue on reverse if necessary and identify by block number)					
<p>The U.S. Army Defense Ammunition Center and School (USADACS). Evaluation Division (SMCAC-DEV). has been asked by MO Industries, Whippany, NJ, to evaluate their 2,200-lb capacity aluminum pallet in accordance with MIL-STD-1660. Design Criteria for Ammunition Unit Loads. The 2,200-lb pallet submitted for testing, MO Industries Part No. 512-1W, with a load capacity of 2,200 lbs, was tested in accordance with MIL-STD-1660 test criteria. The pallet was loaded to 2,200 lbs and subjected to a compression test and a transportation simulation test. Failure occurred in the upright posts connecting the skid to the pallet deck. The upright post punctured through the upper deck frame extrusions. This report details the test procedure, test results, photographic data and conclusions and recommendations for this pallet.</p>					
20. DISTRIBUTION / AVAILABILITY OF ABSTRACT <input type="checkbox"/> UNCLASSIFIED/UNLIMITED <input checked="" type="checkbox"/> SAME AS RPT. <input type="checkbox"/> DTIC USERS			21. ABSTRACT SECURITY CLASSIFICATION UNCLASSIFIED		
22a. NAME OF RESPONSIBLE INDIVIDUAL THOMAS J. MICHELS			22b. TELEPHONE (Include Area Code) AV 585-8928		22c. OFFICE SYMBOL SMCAC-DEV

U.S. ARMY DEFENSE AMMUNITION CENTER AND SCHOOL
Evaluation Division
Savanna, IL 61074-9639

EVT 14-88

MIL-STD-1660 TEST OF
MO INDUSTRIES ALUMINUM
2200 LB. PALLET

TABLE OF CONTENTS

PART	PAGE NO.
1. INTRODUCTION	1-1
A. Background	1-1
B. Authority.	1-1
C. Objective.	1-1
2. ATTENDEES.	2-1
3. TEST PROCEDURES.	3-1
4. TEST EQUIPMENT	4-1
5. TEST RESULTS	5-1
6. CONCLUSIONS AND RECOMMENDATIONS	6-1
7. PHOTOGRAPHS.	7-1

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	



PART 1

INTRODUCTION

A. BACKGROUND. The U.S. Army Defense Ammunition Center and School (USADACS), Evaluation Division (SMCAC-DEV), in coordination with the U.S. Army Armament Research, Development and Engineering Center (ARDEC), SMCAR-AEP, was asked by MO Industries, Whippany, NJ, to test their aluminum pallet, Part No. 512-1W, and evaluate its compatibility to meeting the requirements of MIL-STD-1660.

B. AUTHORITY. This test was conducted in accordance with mission responsibilities delegated by the U.S. Army Armament, Munitions and Chemical Command (AMCCOM).

C. OBJECTIVE. The objective of this test is to assess the MO Industries aluminum pallet for satisfying the capability to meet Army functional/operational requirements of MIL-STD-1660.

PART 2

ATTENDEES

Mr. A. C. McIntosh, Jr.
Test Engineer
AV 585-8989

U.S. Army Defense Ammunition Center and School
ATTN: SMCAC-DEV
Savanna, IL 61074-9639

PART 3

TEST PROCEDURES

The test procedures outlined in this section are extracted from MIL-STD-1660, Design Criteria for Ammunition Unit Loads, 8 April 1977. This standard identifies nine steps that a unitized load must undergo if it is considered to be acceptable. These tests are synopsized below:

1. STACKING TESTS. The unit load shall be loaded to simulate a stack of identical unit loads stacked 16 feet high, for a period of one hour. This stacking load is simulated by subjecting the unit load to a compression of weight equal to an equivalent 16-foot stacking height. The compression load is calculated in the following manner. The unit load weight is divided by the unit load height in inches and multiplied by 192. The resulting number is the equivalent compressive force of a 16 foot high load.
2. REPETITIVE SHOCK TEST. The repetitive shock test shall be conducted in accordance with Method 5019, Federal Standard 101. The test procedure is as follows: The test specimen shall be placed on, but not fastened to, the platform. With the specimen in one position, vibrate the platform at 1/2 inch amplitude (1 inch double amplitude) starting at a frequency of about 3 cycles per second. Steadily increase the frequency until the package leaves the platform. The resonant frequency is achieved when a 1/16-inch-thick feeler may be momentarily slid freely between every point on the specimen in contact with the platform at some instance during the cycle or a platform acceleration achieves one plus or minus zero point one G. Midway into the testing period the specimen shall be rotated 90 degrees and the test continued for the duration. If failure occurs, the total time of vibration shall be two hours

if the specimen is tested in one position; and if tested in more than one position, the total time shall be three hours.

PART 4.

TEST EQUIPMENT

1. TEST SPECIMEN.

- a. Width: 39-1/2 inches
- b. Length: 47-1/2 inches
- c. Height: 38-1/2 inches
- d. Weight: 2,150 pounds

2. COMPRESSION TESTER.

- a. Manufacturer: Ormond Scientific
- b. Platform: 60 inches by 60 inches
- c. Compression Limit: 50,000 pounds
- d. Tension Limit: 50,000 pounds

3. TRANSPORTATION SIMULATOR.

- a. Manufacturer: Gaynes Laboratory
- b. Capacity: 6,000 pound pallet
- c. 1/2-inch Amplitude
- d. Speed: 50 to 3000 cpm
- e. Platform: 5 foot by 8 foot

PART 5

TEST RESULTS

1. STACKING TEST.

Pallet Weight: 2,150 lbs.

Pallet Height: 38-1/2 in.

Test Load Weight: 10,722 lbs.

The test pallet was loaded to 11,000 lbs. compression for a period of one hour. At the end of the one-hour period the compression load decreased to 9,500 lbs and the load compressed approximately 1/4 in. After the pallet was removed from the compression tester, no measurable deformation in the load was evident.

2. REPETITIVE SHOCK TEST. The test pallet failed to pass the longitudinal transportation simulation test. Failure occurred at the attachment point of the end post connecting the skid with the extruded pallet deck. The end post fatigued to a point where it fell into the circumferential molded aluminum pallet frame. In addition to the center post breaking, additional breaks were found after the test at welds on the center posts connecting the skid to the pallet deck.


PART 6

CONCLUSIONS AND RECOMMENDATIONS

1. CONCLUSIONS. The MO Industries 2,200-lb pallet, Part No. 512-1W, was found to be unsatisfactory for the transportation of ammunition. The pallet, though light in weight, does not have sufficient strength to withstand the mechanical vibration expected in a military transport environment.

2. RECOMMENDATIONS. If aluminum pallets are to be considered for use in the transportation of military ammunition, they must satisfactorily meet the criteria of MIL-STD-1660 and its recommended tests. This pallet has a potential of meeting these requirements provided that increased strengthening is accomplished in the pallet. The pallet can expect to see a static load weight of 10,000 lbs. or more and dynamic forces impinging on it of approximately 1G. These 1G forces are described as a sinusoidal pattern with a 1/2' double amplitude for a period of up to three hours.

PART 7
PHOTOGRAPHS

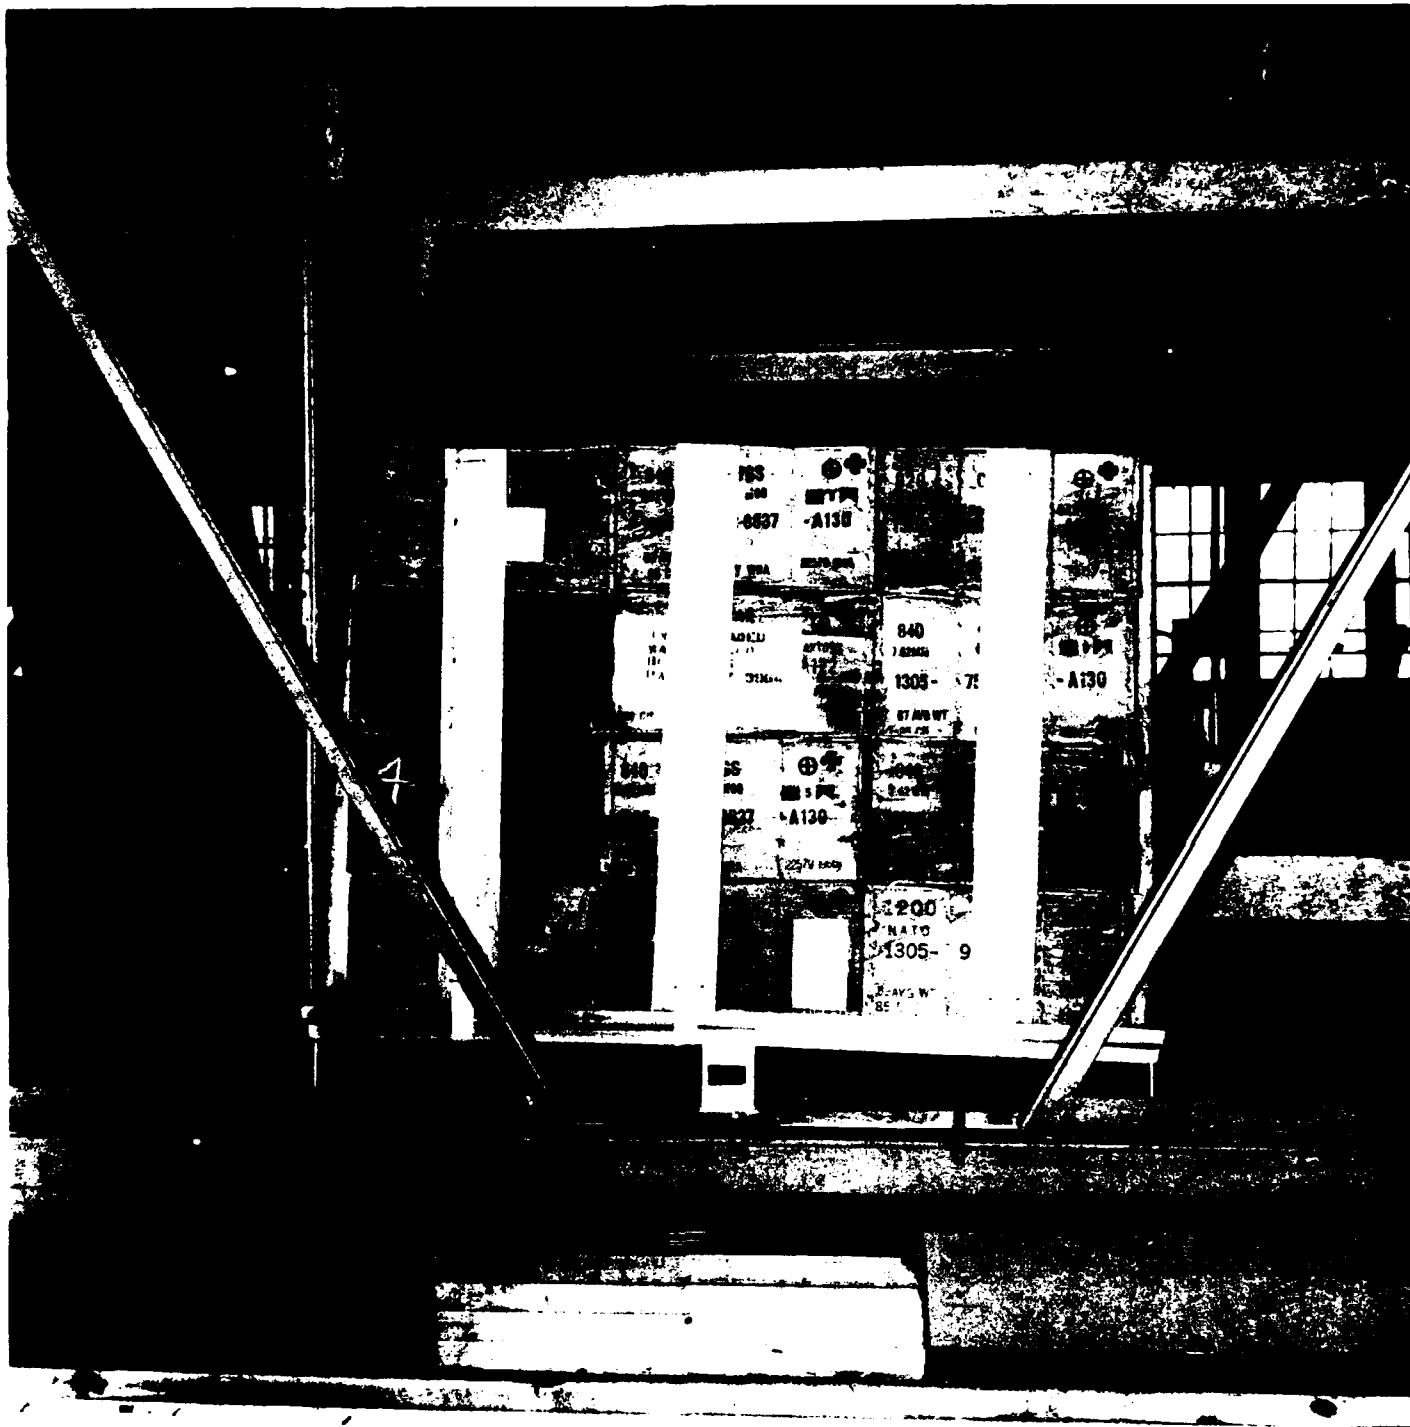

DEFENSE AMMUNITION CENTER AND SCHOOL - SAVANNA, IL

Photo No. 1. This photo shows the MO Industries aluminum pallet in the transportation simulator. Note the right side of the pallet deck is lower than the left side. This is caused by the pallet posts punching through the deck attachment point.



DEFENSE AMMUNITION CENTER AND SCHOOL - SAVANNA, IL

Photo No 2. This photo shows the MO Industries 2,200-lb aluminum pallet where the connecting posts between the skids and the deck have hammered through the attachment point at the upper deck.



DEFENSE AMMUNITION CENTER AND SCHOOL - SAVANNA, IL

Photo No 3. This photo shows the MO Industries 2,200-lb aluminum pallet where the pallet post has punched through the pallet deck on the opposite side.



DEFENSE A. MUNITION CENTER AND SCHOOL - SAVANNA, IL

Photo No 4. This photo shows a crack in the pallet deck frame extrusion just before the pallet post.



DEFENSE AMMUNITION CENTER AND SCHOOL - SAVANNA, IL

Photo No 5. This photo shows the MO Industries 2,200-lb aluminum pallet with a crack in the deck extrusion. All cracks were caused by the transportation simulation test.